



1. Application Sector

DAMTEC® SBM K 20V is an isolation and protection mat for railway track constructions, proofed in accordance to DIN 456735 - mechanical vibrations – resilient element used in railway tracks – part 5: laboratory test procedures for under ballast mats.

Regarding the technical information of DB Netz AG the typical application for thickness 20mm is approved for main line railway with axle loads less than 25 tons and speeds lower than 200 km/h.

Higher axle loads up to 40 tons are suitable if speed is below 80 km/h. Other speeds have to be clarified if the material pressure on the UBM will be higher than 0.30 N/mm².

The sub ballast mat K mat absorbs vibrations and reduces acoustic emission as well as structure borne sound transmission. It is also effective in reducing the frequency of the ballast maintenance requirement through reduced vibration and better-balanced loading. It protects construction and waterproofing.

2. Material

Special mixture of rubber granulate, cellular rubber and PU foam with a PU elastomer bonding agent.

3. Appearance

Colour: Multi coloured

Surface: Granular texture surface is laminated with geotextile, white

4. Dimensions/Tolerances

Width:	1,250 mm	± 1.5 %
Length:	4,000 mm	± 1.5 %
Thickness:	20 mm	± 1.0 mm
Area weight:	approx. 13.0 kg/m ²	

(slabs and other lengths are possible on request for special projects)

5. Aptitude Test

Test in accordance to E DIN 45673-5 (DBS 918071) at Technical University Munich, Technical University Dresden and at Müller BBM in Planegg.

6. Installation


The installation has to be in accordance to installation instructions **DAMTEC® SBM K**. Note that with application and installation for DB AG (German Railway) guidelines for sub ballast mats, „Unterschottermatten einbauen“ (824.1510), have to be observed.

For structure borne noise insulation and isolation of secondary airborne noise an adhesion is not necessary.

7. Test Data

Tensile strength:	0.15 - 0.55 N/mm ² (ISO 1798)
Elongation at break:	40 - 70 % (ISO 1798)
Burning behaviour:	E (EN 13501-1)
Thermal resistance:	- 30°C to + 80°C
Chemical resistance:	Conditionally resistant to acids and bases
Environmental resistance:	Oil-, aging-, rot-resistant and water-resistant
Static bedding modulus (Cstat1):	0.06 N/mm ³ ± 15%
Static bedding modulus (Cstat2):	0.061 N/mm ³

Influence of temperature on Cstat:

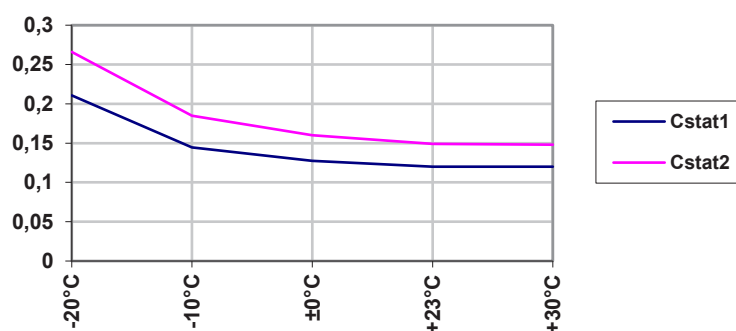

Dynamic bedding modulus (Cdyn1): ($\sigma_1 = 0.02 \text{ N/mm}^2$; $\sigma_2 = 0.10 \text{ N/mm}^2$)

0.077 N/mm³ (bei 1 Hz) ±15%

0.092 N/mm³ (bei 5 Hz) ±15%

0.099 N/mm³ (bei 10 Hz) ±15%

0.107 N/mm³ (bei 20 Hz) ±15%

0.113 N/mm³ (bei 30 Hz) ±15%


(at -20°C) Cdyn1(10Hz) = 0.386 N/mm³

(at -10°C) Cdyn1(10Hz) = 0.232 N/mm³

(at ±0°C) Cdyn1(10Hz) = 0.153 N/mm³

(at +30°C) Cdyn1(10Hz) = 0.094 N/mm³

Dynamic bedding modulus (Cdyn2):

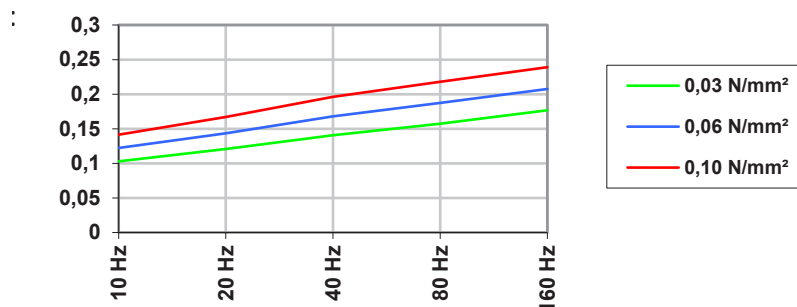

[no difference within the results for LV =100dB and LV =90dB]

Horizontal static modulus (G_{stat}):	0.021 N/mm ³
Horizontal deflection:	$s = 0.26\text{mm} < 0.4\text{mm}$
Mechanical fatigue strength:	Load phase 1 – $F_O/F_U = 75/10\text{kN}$ – 10 million load changes Load phase 2 – $F_O/F_U = 100/10\text{kN}$ – 2.5 million load changes (before load phase 1) $C_{stat1} = 0.062\text{N/mm}^3$ $C_{stat2} = 0.065\text{N/mm}^3$ (after load phase 1) $C_{stat1} = 0.063\text{N/mm}^3$ $C_{stat2} = 0.071\text{N/mm}^3 + 1.6\%$ (after load phase 2) $C_{stat1} = 0.063\text{N/mm}^3$ $C_{stat2} = 0.070\text{N/mm}^3 + 1.6\%$ [After 12.5 Mio. load changes DAMTEC® SBM K slightly impressions due to the contact with the ballast. Not any cracks and perforations could be detected with the naked eye.]
Water / frost resistance:	-20 % for dynamic stiffness
Resistance for aging:	Change of static stiffness +6% at 23°C Change of static stiffness +7% at -20°C Change of weight -0,16%
Resistance to oil:	After 7 days in mineral oil: tensile strength: average 0.31N/mm ² elongation at break: average 43.16%

Static stiffness for different load ranges:

max. load	secant modulus		C_{stat1}	secant modulus		C_{stat2}
[N/mm ²]	[N/mm ²]	[N/mm ²]	[N/mm ³]	[N/mm ²]	[N/mm ²]	[N/mm ³]
0.15	0.02	0.06	0.060	0.02	0.12	0.062
0.20	0.02	0.08	0.059	0.02	0.16	0.061
0.25	0.02	0.10	0.057	0.02	0.20	0.062
0.35	0.02	0.14	0.056	0.02	0.28	0.066

8. Accessories

- Adhesive tape: Gerband 613

9. Approval

- Conforms to the ASA and TfNSW Standard for Ballast (T HR TR 00192 ST), Section 11.6.
Track stiffness and ballast mat.
- Approved according to the Deutsche Bahn standards

The use of under ballast mat **DAMTEC® SBM K 20V** for ballasted track was approved by DB Netz AG in an individual case-related technical note under the TM-titel 2011-1022 I.NVT 4 to Ril 82002010 and Ril 824.1510.

The approval shall apply provisionally to operational testing. During testing, each application requires the consent of DB Netz, Zentrale, I.NVT 41.

Contact information:

Manufactured by KRAIBURG Relastec GmbH & Co.KG

Distributed in Australia by Projex Group Pty Ltd.

PO Box 98, Matraville NSW 2036

+61 2 8336 1666

mail@projex.com.au

**DISCLAIMER:**

This information is based on our tests and experiences and is provided to the best of our knowledge and beliefs. However, KRAIBURG RELASTEC does not guarantee in each individual case the use and processing results of its **DAMTEC®** products, due to the huge number of various fields of application as well as storage, processing or construction conditions which are beyond our control. Own tests are to be conducted. Please contact our technical customer service for any further advice.

The data sheet is not subject to any change service! All information is without guarantee.
With the publication of this product data sheet all former issues cease to be valid.